


Polymer Chemistry

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: A. Jäger, E. Jäger, F. Surman, A. Höcherl, B. Angelov, K. Ulbrich, M. Drechsler, V. M. Haramus, C. Rodriguez-Emmenegger, F. Nallet and P. Stepanek, *Polym. Chem.*, 2015, DOI: 10.1039/C5PY00567A.

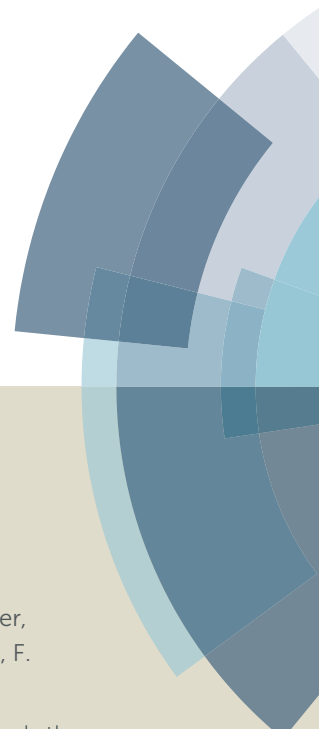

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

Nanoparticles of poly([N-(2-hydroxypropyl)]methacrylamide)-*b*-poly[2-(diisopropylamino)ethyl methacrylate] diblock copolymer for pH-triggered release of paclitaxel

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Alessandro Jäger,^{a,*} Eliézer Jäger,^{a*} František Surman,^a Anita Höcherl,^a Borislav Angelov,^a Karel Ulbrich,^a Markus Drechsler,^b Vasil M. Garamus,^c Cesar Rodriguez-Emmenegger,^{a,*} Frédéric Nallet^d and Petr Štěpánek^a

The potential of self-assembled nanoparticles (NPs) containing the fine tunable pH-responding property of the hydrophobic poly[2-(diisopropylamino)ethyl methacrylate] (PDPA) core and the protein repellence of the hydrophilic poly[N-(2-hydroxypropyl)methacrylamide] (PHPMA) shell on *in-vitro* cytostatic activity has been explored on cancer cells. The amphiphilic diblock copolymer poly[N-(2-hydroxypropyl)methacrylamide]-*b*-poly[2-(diisopropylamino)ethyl methacrylate] (PHPMA-*b*-PDPA) synthesized by reversible addition-fragmentation chain transfer (RAFT) technique which allows excellent control of polymer chain length for methacrylamides. The PHPMA-*b*-PDPA block copolymer dissolved in organic solvent (ethanol/dimethylformamide) undergoes nanoprecipitation in phosphate buffer saline (PBS, pH ~ 7.4) and self-assembles into regular spherical NPs after solvent elimination. The NPs structure was characterized in detail by dynamic (DLS), static (SLS) and electrophoretic (ELS) light scattering, small angle X-ray scattering (SAXS), and cryo-transmission electron microscopy (cryo-TEM). The PHPMA chains prevented the fouling of proteins resulting in a remarkable stability of the NPs in serum. On decreasing pH the hydrophobic PDPA block becomes protonated (hydrophilised) in the narrow range of pH (6.51 < pH < 6.85; ΔpH ~ 0.34) resulting in the fast disassembly of the NPs and chemotherapeutic drug release at simulated acidic environment in endosomal and lysosomal compartments. Minimal amount of drug was released above the threshold pH of 6.85. The *in-vitro* cytotoxicity studies showed an important increase in activity of the NP-loaded with drug compared to the free drug. The particle's size below the cut-off size of the leaky pathological vasculature (less than 100 nm), the excellent stability in serum and the ability to release a drug at the endosomal pH with concomitant high cytotoxicity makes them suitable candidates for cancer therapy, namely for treatment of solid tumours exhibiting high tumor accumulation of NPs due to Enhanced Permeability and Retention (EPR) effect.

Introduction

A great deal of attention has been paid to block copolymers that when exposed to an aqueous environment self-assemble into highly organised nanoscale structures.^{1,2} By changing the solvent selectivity or the insoluble-to-soluble block length ratio, one obtains thermodynamically favoured structures of various morphologies in solution.³ Typical morphologies such as spheres, rods, lamellae and vesicles (polymersomes) can be easily prepared in a controlled manner in aqueous solutions through the self-assembly of asymmetric amphiphilic diblock copolymers.⁴ Characterised by a

bulky core and a relatively thin corona the particles made by the self-assembly of highly asymmetric diblocks are frozen structures and do not dissociate under dilution.⁵ Some of these structures such as spheres and vesicles have attracted attention as versatile carriers for drug delivery.^{6,7} They present improved colloidal stability under physiological conditions when compared to water soluble amphiphilic micelles and the ability to encapsulate or integrate a broad range of drugs. However, several problems arise related to the slow drug release if the drug is encapsulated in frozen colloidal particles, especially for applications such as drug release in cancer therapy. For an optimal therapy the hydrophobic guest drug molecules have to be seized into the inner particle core during circulation in the bloodstream and be quickly released at the specific tumour sites.⁸ Recently, several types of pH-sensitive polymeric NPs have been investigated for such purpose^{9,10} because the extracellular pH in most solid tumour tissues is more acidic (ranging from pH 6.7 to 7.1),^{11,12} compared to the normal tissues (buffered at pH 7.4). Furthermore, variations in pH are also encountered when nanoparticles are internalized by cells via

^a Institute of Macromolecular Chemistry v.v.i., Academy of Sciences of the Czech Republic, Heyrovsky Sq. 2, 162 06 Prague 6, Czech Republic. E-mail: ajager@imc.cas.cz; jager@imc.cas.cz and rodriguez@imc.cas.cz

^b Laboratory for Soft Matter Electron Microscopy, Bayreuth Institute of Macromolecular Research, University of Bayreuth, D-95440 Bayreuth, Germany.

^c Helmholtz-Zentrum Geesthacht, Centre for Materials and Coastal Research, D-21502 Geesthacht, Germany.

^d Centre de Recherches Paul-Pascal, CNRS, Université de Bordeaux, 115 Avenue Schweitzer, F-33600 Pessac, France.

* Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See

DOI: 10.1039/x0xx00000x

ARTICLE

Journal Name


endocytosis where the pH usually drops to as low as 5.0 - 6.0 in endosomes and 4.0 - 5.0 in lysosomes.¹³

For such challenging task, taken into account the small pH window ($\Delta\text{pH} \sim 0.4$) in which the drug must be released, the 2-(diisopropylamino)ethyl methacrylate (DPA) based copolymers have recently proved to be valuable tools capable of fine tuning the release in the desired pH region, both in *in-vitro*¹⁴ and *in-vivo*¹⁵ and quickly release the drug independently of its hydrophobicity¹⁶ or hydrophilicity.¹⁷ Nevertheless, regardless of the efficiency of the trigger mechanism involved in the drug release towards a successful cancer therapy the nanocarrier must reach the tumor tissue first. However, nanoparticles in contact with blood stream are rapidly coated with a corona of proteins which can impair the colloidal stability or can cause the particle to be eliminated *via* phagocytosis. This can only be circumvented by the engineering the nanocarrier system to be "stealth" with a low particle size (between 10 and 100 nm) having a sufficiently long circulation time to undergo passive specific accumulation in the tumor tissue through the EPR effect.¹⁸ Recently published results from our group have demonstrated that unlike poly(ethylene glycol) PEG,¹⁹ brushes of poly[N-(2-hydroxypropyl)methacrylamide] (PHPMA) withstand the fouling from blood plasma²⁰ and full blood.²¹ The unmatched performance of PHPMA was also utilized to improve the circulation of hydrophobic nanoparticles with PHPMA-modified surfaces *in-vitro*²² and *in-vivo*²³.

Herein, for the first time, the potential of self-assembled NPs containing the fine tunable pH-responsing property of the hydrophobic poly[2-(diisopropylamino)ethyl methacrylate] (PDPA) core and protein repellence of the hydrophilic PHPMA shell on *in-vitro* cytostatic activity tested on cancer cells are reported. A diblock copolymer composed of hydrophobic PDPA and hydrophilic PHPMA was prepared by RAFT polymerisation. Poly[N-(2-hydroxypropyl)methacrylamide]-*b*-poly[2-(diisopropylamino)ethyl methacrylate] (PHPMA₂₅-*b*-PDPA₁₀₆) assembled forming nanoparticles. The novel NPs self-assembly and structure were characterized in detail by cryo-TEM, SAXS, DLS, SLS and ELS light scattering techniques. Acidic physiological conditions trigger the disassembly of the novel NPs prepared from the block copolymer PHPMA₂₅-*b*-PDPA₁₀₆ thus controlling release of their cargo, the chemotherapeutic paclitaxel (PTX), which results in a high cytostatic effect on HeLa cancer cells in *in-vitro* studies.

Results and discussion

The block copolymer was prepared using RAFT polymerisation. A first block of PHPMA, $M_n = 3\,600\text{ g}\cdot\text{mol}^{-1}$, $M_w/M_n = 1.07$; Scheme 1, Fig. S1 and S2) was synthesised and used as macro chain transfer agent. Subsequently a long second block of PDPA ($M_n = 26\,200\text{ g}\cdot\text{mol}^{-1}$, $M_w/M_n = 1.29$) was grown from the macroCTA also by RAFT. RAFT polymerisation accounts for excellent living characteristic in the polymerization of methacrylamides. The block copolymer comprising a hydrophobic block (PDPA) and a hydrophilic block (PHPMA) favours the formation of stable NPs with a bulky core capable of encapsulating and controlling the release of the hydrophobic chemotherapeutic PTX.

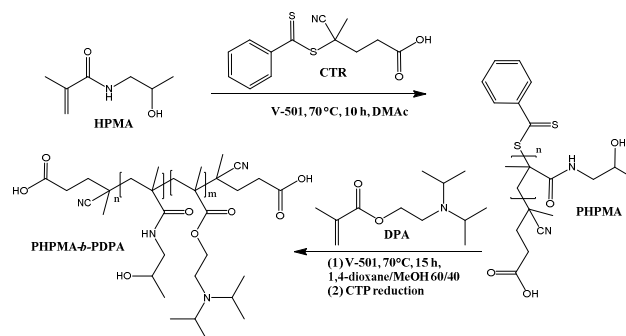

Scheme 1. Synthetic route and molecular structure of the PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer with pH-triggered assembly/disassembly.

The hydrophilic corona of PHPMA was utilized to protect the hydrophobic core from adsorption of proteins from blood (*vide infra*). An abrupt change in the light scattering intensity was observed during the titration experiments of the PHPMA₂₅-*b*-PDPA₁₀₆ diblock copolymer in aqueous solution simulating physiological conditions. The hydrophobic DPA block is protonated (hydrophilised) in the narrow range of pH ($6.51 < \text{pH} < 6.85$; $\Delta\text{pH} \sim 0.34$, Fig. 1a).

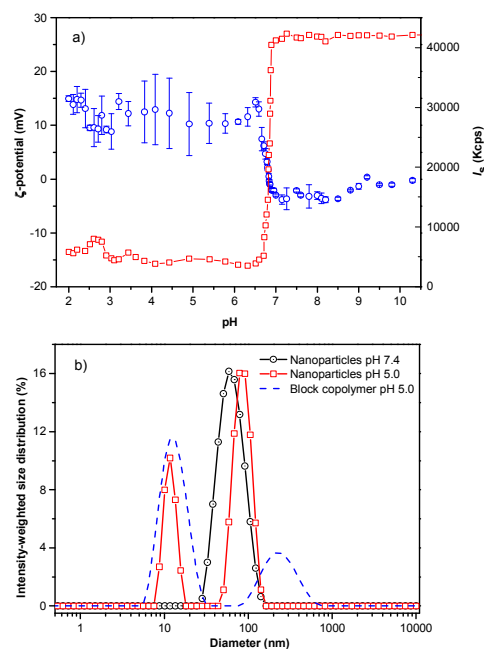


Fig. 1 (a) Potentiometric acid-base titration curve for the PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer as a function of overall scattering intensity (red squares) and zeta potential values (black circles) and (b) intensity-weighted size distribution for the PHPMA₂₅-*b*-PDPA₁₀₆ NPs at pH 7.4 (black circles) for the nanoparticles at pH 5.0 (red squares) and the single block copolymer at pH 5.0 (blue dashed lines) and angle 173° at concentration of 1 mg·mL⁻¹ diluted in PBS at 37 °C.

The markedly narrow window of pH at which the diblock copolymer (namely DPA block) can be protonated and the large change in scattering intensity and hydrodynamic diameter suggest that pH is a remarkably effective and precise trigger for assembly and disassembly of the system. The NPs were prepared by the solvent-shifting method, whereby PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer was dissolved in ethanol or dimethylformamide (concentration ~ 1 mg·mL⁻¹) and phosphate buffer saline (PBS, pH ~ 7.4) was added dropwise to the organic solution under stirring until the aqueous weight fraction reached twice the weight of the organic phase. The organic solvent was removed by dialysis or evaporated under reduced pressure. DLS measurement of the diblock copolymer (before NP formation) in ethanol shows that most chains were fully dissolved with an average hydrodynamic diameter of $2R_H = 9.0$ nm (Fig. 1b).

After PBS addition and solvent evaporation the DLS shows a monomodal average size distribution referred to the NPs population ($2R_H = 52$ nm, Fig. 1b, black circles) with low dispersity as was estimated by using the cumulant analysis ($\mu^2/I^2 = 0.120 \pm 0.009$), and as observed by Cryo-TEM (Fig. 2a). At pH 7.4 (PBS buffer) the average ζ -potential for the studied block copolymer nanoparticles is close to neutrality (~ -2.5 mV) (Fig. 1a). Decreasing the pH below the pKa (DPA) ($6.51 < \text{pH} < 6.85$) the system is rapidly protonated as evidenced by the positive ζ -potential and mainly composed of molecularly dissolved block copolymer chains besides a very small number of large aggregates ($R_H \sim 125$ nm). This aggregates represent about 25% of the intensity-weighted distribution, thus following the relationship $I_{sc} \sim c \cdot R^3$ the number of large particles can be calculated to be 0.0025 % of the total number of objects scattering light in the system¹⁶ (Fig. 1b). This negligible number of aggregates can be clearly visualized in the volume-weighted distribution of R_H shown in Fig. S5.

Cryo-TEM images obtained at pH 7.4 reveal well-defined spherical NPs (Fig. 2a). The SAXS profile of the PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer NPs (Fig. 2b) indicates the presence of flexible polymer chains described by a Gaussian statistics at the outermost layer of the particles as evidenced at the high- q range profile corresponding to the PHPMA chains. These chains are, however, not visible by Cryo-TEM image (Fig. 2a) due to poor contrast. To model the SAXS profile we utilized a superposition of Gaussian chains as a background and spherical nanoparticles:

$$I(q) \sim K^2(q, R, \Delta n) + \text{background}, \text{ (eq. 1)}$$

where,

$$K(q, r, \Delta n) = \frac{4}{3} \pi R^3 \Delta n^2 \frac{\sin(qR) - qR \cos(qR)}{(qR)^3}, \text{ (eq. 2)}$$

is the scattering from spherical NPs of radius R , Δn is the difference between the scattering length density of the polymer and the solvent. Similar model was used previously to describe diverse systems.^{23,24} The obtained nanoparticle radius $R \sim 23$ nm (diameter = $2R_H = 46$ nm) is in good agreement with the DLS and Cryo-TEM data. Similarly, SLS measurements of NPs at pH = 7.4 (Fig. S3) shows a $R_G = 24$ nm and $M_w \sim 1.2 \times 10^6$ g·mol⁻¹.

The R_G/R_H ratio obtained by SLS and DLS data, gave access to the structural characteristics of the particles. It is well established that the NPs R_G/R_H ratio values of 0.775, 1.78, and ≥ 2 have been reported for hard spheres, random coils and rod-like structures, respectively.^{16,22,23,26} Furthermore, the R_G/R_H ratio of spherical objects depends on their inner structure and compactness, being close to 0.775 for compact spheres, 0.8-0.9 for block copolymer micelles due to solvation phenomena and 1.0 for hollow spheres and vesicles.^{16,23,26} The R_G/R_H ratio found for the PHPMA₂₅-*b*-PDPA₁₀₆ NPs ($R_G/R_H \sim 0.92$) indicates that the particles had a core-shell-like structure.^{16,27} Therefore, the most probably structural arrangement of the PHPMA₂₅-*b*-PDPA₁₀₆ NPs is a particle composed of PDPA core surrounded by a PHPMA shell. These findings are in agreement with the SAXS measurements which identify polymer chains with Gaussian configuration at the outer region of the NPs. Furthermore, aggregation numbers with the same order of magnitude (~ 46 chains per particle) were also found for particles with such structural composition.^{16,24,27}

The efficient NPs accumulation in the solid tumor tissue requires an extended circulating capability to enable a time-dependent extravasation of the NPs through the leaky tumor microvasculature (EPR effect). Therefore, long-term stability of the NPs in serum is a pre-requisite for the use of polymer NPs *in-vivo*.^{23,28,29} As a model of the possible detrimental interaction of the nanoparticles with proteins from blood we incubate them in human plasma (10% in PBS). The stability of the NPs was monitored by evaluating any possible changes in their hydrodynamic size and scattering intensity over time.^{23,26,29} Fig. 3a shows the temporal stability of the NPs in diluted human blood plasma as a function of the incubation time.

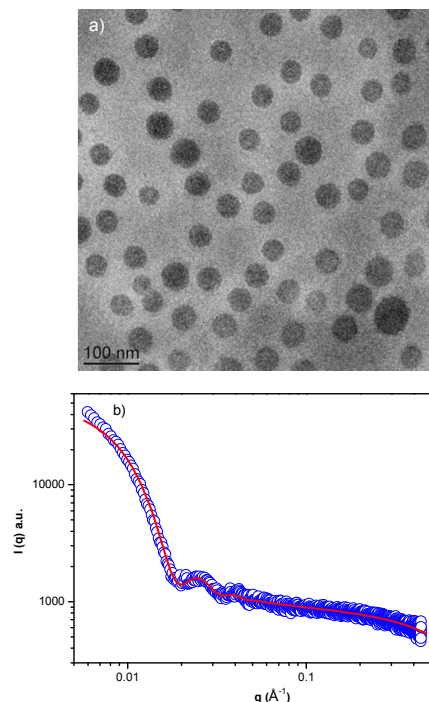


Fig. 2 Cryo-TEM image of the block copolymer NPs (a) and (b) small angle X-ray scattering profile in PBS, pH 7.4.

ARTICLE

Journal Name

The size and scattering intensity patterns of the NPs do not change within the studied 36 h suggesting that the NPs are stable in the simulated but highly challenging media. The high stability of the NPs is based on their hydrophilic shell nature-improved colloidal stability-and by its unmatched resistance to protein adsorption.^{16,20,29} By preventing any adsorption of proteins the NPs are virtually “invisible” for the blood milieu in which makes them a promising system for *in-vivo* applications.^{23,29-31}

Subsequently, the release profile of the chemotherapeutic PTX was investigated under conditions mimicking the acidic environment in endosomal and lysosomal compartments, pH ~ 5 and 37 °C. The release experiments at 37 °C were conducted also at pH 7.4 to simulate conditions during transport in blood and in normal healthy tissues (Fig. 3b). The drug release profile is clearly pH-sensitive in accordance with the physico-chemical studies presented above.

The results suggest that at pH ~ 5.0 (acidic environment in endosomal and lysosomal compartments) the block copolymer becomes protonated: becomes a polycation. The Coulombic repulsion among the chains disrupts the NPs which physically disassemble (pH-triggered disassembly, Fig. 1 and 3b), thus resulting in a 3.5 fold acceleration of the rate of release of the chemotherapeutic (~ 70 %) within 24 h, (pH ~ 5.0) compared to physiological conditions (PBS). Moreover, ~ 21 % of the drug was released from the intact NP cores when kept in PBS at pH 7.4. The release data demonstrate that during the systemic circulation

minimal quantity of the drug would be released before reaching the solid tumor environments *via* the EPR effect. Conversely, the chemotherapeutic is readily released at pH 5.0 with ~ 70 % of the loaded anticancer drug released within first 24 h fulfilling the criteria³² for a pH-triggered drug release mechanism exhibiting practical application as nanocarriers in passive tumor-targeted drug delivery.

To investigate the inhibitory effect on tumor cells, the pH-triggered PHPMA₂₅-*b*-PDPA₁₀₆ NPs were loaded with the antitumor drug PTX with an overall cargo rate around 2.5 wt % and a loading efficiency of 96 % (see Mat. and Methods). Given the high loading (negligible free PTX) no further purification was carried out. The cell viability assay using alamarBlue[®] was used to examine the *in-vitro* cytotoxicity as a classical approach to evaluate the direct effect of the drug-loaded NPs on target cancer cells. The HeLa cell line was selected as a widely used and well-studied cancer cell model system. The drug-loaded NPs were incubated with the HeLa cells for 24 and 48 h. The *in-vitro* cell viability experiments demonstrated that the PTX-loaded-PHPMA₂₅-*b*-PDPA₁₀₆ NPs exhibited a similar if not slightly stronger cytotoxic effect as the free drug after 24 h of incubation (Fig. 4a). After the incubation over 48 h the superior toxicity of the PTX-loaded-PHPMA₂₅-*b*-PDPA₁₀₆ NPs compared to free PTX is clearly visible (Fig. 4b). The NPs (IC₅₀ 0.1 ng·mL⁻¹) exhibited significantly higher cytotoxicity than the free PTX (IC₅₀ 1.7 ng·mL⁻¹) which corresponds to values stated in the literature for HeLa cells.^{33,34} This increased cytotoxicity of the drug-carrying NPs compared to the

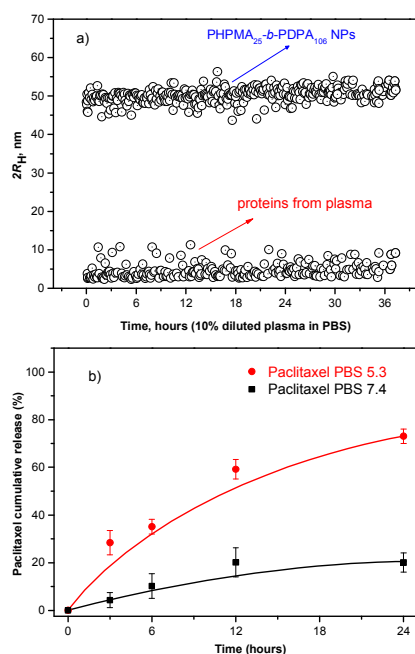


Fig. 3 (a) Size distribution in dissolved human plasma (10% v/v in PBS) for the PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer NPs in function of the incubation time and (b) drug release profiles from paclitaxel-loaded PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer NPs at pH 7.4 (PBS, closed black squares) simulating transport in blood and at pH 5.3 (PBS, closed red circles) simulating the acidic environment in endosomal and lysosomal compartments at 37 °C.

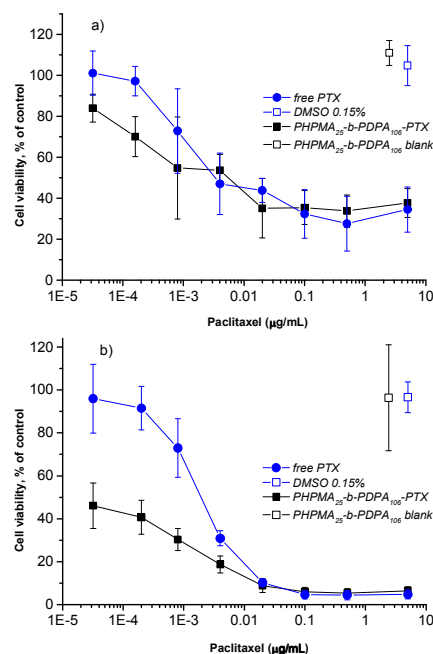


Fig. 4 Cell viability of HeLa cell line after 24 h (a) and 48 h (b) incubation with different concentrations of free PTX (closed blue circles) and PTX-loaded PHPMA₂₅-*b*-PDPA₁₀₆ (closed black squares) NPs. DMSO 0.15% (open blue squares) and blank PHPMA₂₅-*b*-PDPA₁₀₆ NPs (open black squares) were used as controls.

free drug has been previously reported for analogous systems³⁵⁻³⁹ and is supposedly the result of enhanced endocytotic uptake of NPs. In particular at low drug concentrations and higher incubation times (below 0.005 $\mu\text{g}\cdot\text{mL}^{-1}$, Fig. 4b) the endocytotic uptake of the PTX-loaded NPs is more efficient than the uptake of free drug into the cells.³⁶ A strong toxicity of the drug-loaded NPs after 48 h incubation correlates with the hypothesis, that a significant amount of particles is already internalized in endosomal compartments within the first 24 h – and that this is closely followed by a fast release of the drug (within 24 h approx. 70% of the drug was released under acidic conditions mimicking conditions in endosomal and lysosomal compartments, see Fig. 3b). Drug-free PHPMA₂₅-*b*-PDPA₁₀₆ NPs were also tested up to the applied maximal concentration (0.4 $\text{mg}\cdot\text{mL}^{-1}$) with no significant cytotoxic activity (Fig. 4a and 4b, Fig. S4A and Fig. S4B). After disassembly of the nanoparticles (pH < pK_A), the freely dissociated PHPMA₂₅-*b*-PDPA₁₀₆ chains present protonated amine groups to the cell. Toxicity of protonated amine groups has been described previously.⁴⁰ This may contribute to the high toxicity of the presented system. However, the data clearly showed evidenced that the drug-free PHPMA₂₅-*b*-PDPA₁₀₆ particles have no relevant observable toxic effect to the cells (Fig. 4a and 4b, Fig. S4A and S4B). Therefore the high efficiency of the drug delivery system is purely attributed to the efficient transport and release of the drug, and side effects of material toxicity can be excluded. It is important to highlight that the extracellular pH differences between the tumoral tissues and the healthy tissues are not just a characteristic of tumors but also ischemia, inflammation, renal failure or chronic obstructive pulmonary diseases that share also similar pH differences to their healthy counterparts. Therefore the HPMA-*b*-PDPA copolymer NPs may also find applications as drug carriers for their treatment.

Conclusions

In summary a diblock copolymer of PHPMA and PDPA was prepared by RAFT polymerisation. The diblock copolymer was assembled into spherical NP consisting of a core of PDPA and a corona of PHPMA as evidenced by SLS, cryo-TEM and SAXS. Presumably, the PHPMA chains prevented the fouling from proteins resulting in a remarkable stability in serum. Reduction of the pH below 6.85 resulted in a rapid increase in the zeta-potential and the fast disassembly of the particle (size decrease in DLS). This was exploited as a trigger for the delivery of hydrophobic drugs into cancer cells. Minimal amount of drug was released above the threshold pH. The *in-vitro* cytotoxicity studies showed an important increase in activity of the NP-loaded with drug compared to the free drug. The particle's size below the cut-off size of the leaky pathological vasculature ($2R_H < 100 \text{ nm}$), the excellent stability in serum and the ability to release a drug at the endosomal pH with concomitant high cytotoxicity makes them suitable candidates for cancer therapy, namely for treatment of solid tumours exhibiting high tumor accumulation of NPs due to effective EPR effect.

Experimental section

Materials

Monomer 2-(Diisopropylamino)ethyl methacrylate (DPA, 97 %) was purified by vacuum distillation prior to use. Monomer *N*-(2-hydroxypropyl)methacrylamide (HPMA) was synthesized according to the reference.⁴¹ Initiator 4,4-azobis(4-cyanopentanoic acid) (V-501, Aldrich) was recrystallized from methanol prior to use. Chain transfer agent 4-cyano-4-(phenylcarbonothioylthio)pentanoic acid (CTP, Aldrich) was used as received. Solvents, methanol, dimethylacetamide and 1,4-dioxane were purchased from Lach-ner, dried over molecular sieves (3 Å) and distilled prior to use.

Methods

¹H NMR

The ¹H NMR spectra were recorded using a Bruker AMX-300 300 MHz spectrometer. PHPMA was dissolved in D₂O and PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer in D₂O/DCI (pH 2).

Size exclusion chromatography (SEC)

The number-average molecular weight (M_n) and its distribution (M_w/M_n) were obtained by SEC. SEC of the isolated copolymers was performed at 25°C with two PLgel MIXED-C columns (300 × 7.5 mm, SDV gel with particle size 5 μm ; Polymer Laboratories, USA) and with UV (UVD 305; Watrex, Czech Republic) and RI (RI-101; Shodex, Japan) detectors. The mixture of tetrahydrofuran/methanol 80/20 v/v % was used as a mobile phase at a flow rate of 1 $\text{mL}\cdot\text{min}^{-1}$. The molecular weight values were calculated using Clarity software (Dataapex, Czech Republic). Calibration with PMMA standards was used. The absolute number-average molar mass (M_n) molar mass distribution (M_w/M_n) of PHPMA macroCTA was determined on a HPLC Shimadzu system equipped with Superose 12TM column, UV, Optilab rEX differential refractometer and multiangle light scattering DAWN 8 (Wyatt Technology, USA) detectors. For these experiments, the 0.3 M sodium acetate buffer (pH 6.5) containing 0.5 $\text{g}\cdot\text{L}^{-1}$ sodium azide was used as the mobile phase.

Synthesis of PHPMA macroCTA

In a Schlenk flask equipped with magnetic stirrer bar, HPMA monomer (3 g, 21 mmol) and CTP (94 mg, 0.34 mmol) were dissolved in 17 mL of DMAc and deoxygenated by four freeze-pump-thaw cycles. Subsequently, 300 μL (0.167 mmol) of the initiator V-501 solution (78 mg, 0.5 mL DMAc) was added and another one freeze-pump-thaw cycle was performed. The flask containing pink solution was filled with argon and placed into the oil bath (70°C) to start the polymerisation. After 10 h, the polymerisation was quenched by exposing the reaction mixture to air and liquid nitrogen. The polymerisation solution was precipitated in diethylether/acetone (3/1) mixture, filtrated and vacuum dried to yield a pink solid (875 mg). The conversion was 36% as determined from ¹H NMR spectroscopy (Fig. S1B). The obtained polymer was characterized by SEC $M_n = 3600 \text{ g}\cdot\text{mol}^{-1}$, $\bar{D} = 1.07$ (Fig. S1A).

Synthesis of poly(*N*-(2-hydroxypropyl)methacrylamide)-*b*-(2-(diisopropylamino)ethyl methacrylate) (PHPMA₂₅-*b*-PDPA₁₀₆)

In a Schlenk flask equipped with magnetic stirrer bar, PHPMA macroCTA (432 mg, M_n 3600, \bar{D} 1.07) was dissolved in MeOH (3 mL). The monomer DPA (2.56 g, 12 mmol) and 1,4-dioxane (4 mL) were added and the mixture was deoxygenated by four freeze-pump-thaw cycles. Subsequently, 100 μL (0.039 mmol) of the

ARTICLE

Journal Name

initiator V-501 solution (33 mg, 0.3 mL DMAc) was added and another one freeze-pump-thaw cycle was performed. The flask containing pink solution was filled with argon and placed into the oil bath (70 °C) to start the polymerisation. After 15 h, the polymerisation was quenched by exposing the reaction mixture to air rapidly colling in liquid nitrogen. The polymer was isolated by dialysis using SpectraPor dialysis membrane MWCO 3500 against water (pH 2-3) for five days. The solution of polymer was lyophilized to yield light pink solid. The conversion was 94% as determined from ^1H NMR spectroscopy. The dithiobenzoic ω -end group was removed by the method introduced by Perrier⁴¹ using V-501 and polymer isolated by dialysis and lyophilization to obtain white solid. The obtained polymer was characterised by SEC $M_n = 26\,200\text{ g}\cdot\text{mol}^{-1}$, $\bar{D} = 1.29$. The synthetic parameters and molecular weight data of polymers prepared via RAFT polymerization are described in Table TS1 (ESI).

Scattering techniques

The dynamic light scattering (DLS) measurements were performed using an ALV CGE laser goniometer consisting of a 22 mW HeNe linear polarized laser operating at a wavelength ($\lambda = 632.8\text{ nm}$), an ALV 6010 correlator, and a pair of avalanche photodiodes operating in the pseudo cross-correlation mode. The samples were loaded into 10 mm diameter glass cells and maintained at $25 \pm 1\text{ }^\circ\text{C}$. The data were collected using the ALV Correlator Control software and the counting time was 30 s. The measured intensity correlation functions $g_2(t)$ were analysed using the algorithm REPES (incorporated in the GENDIST program)⁴³ resulting in the distributions of relaxation times shown in equal area representation as $\tau A(\tau)$. The mean relaxation time or relaxation frequency ($\Gamma = \tau^{-1}$) is related to the diffusion coefficient (D) of the nanoparticles as $D = \frac{\Gamma}{q^2}$ where $q = \frac{4\pi n \sin \frac{\theta}{2}}{\lambda}$ is the scattering vector being n the refractive index of the solvent and θ the scattering angle. The hydrodynamic radius (R_H) or the distributions of R_H were calculated by using the well-known Stokes-Einstein relation:

$$R_H = \frac{k_B T}{6\pi\eta D} \quad (\text{eq. 3})$$

being k_B the Boltzmann constant, T the absolute temperature and η the viscosity of the solvent.

In the static light scattering (SLS), the scattering angle was varied from 30 to 150° with a 10° stepwise increase. The absolute light scattering is related to weight-average molar mass ($M_w(\text{NP})$) and to the radius of gyration (R_g) of the nanoparticles by the Zimm formalism represented as:

$$\frac{K_c}{R_\theta} = \frac{1}{M_w(\text{NP})} \left(1 + \frac{R_g^2}{3} q^2 \right) \quad (\text{eq. 4})$$

where K is the optical constant which includes the square of the refractive index increment (dn/dc), R_θ is the excess normalized scattered intensity (toluene was applied as standard solvent) and c is the polymer concentration given in $\text{mg}\cdot\text{mL}^{-1}$. The refractive index increment (dn/dc) of the PHPMA₂₅-*b*-PDPA₁₀₆ NPs in PBS

(0.143 $\text{mL}\cdot\text{g}^{-1}$) was determined using a Brice-Phoenix differential refractometer operating at $\lambda = 632.8\text{ nm}$.

The small angle X-ray scattering (SAXS) experiments were performed on the P12 BioSAXS beamline at the PETRA III storage ring of the Deutsche Elektronen Synchrotron (DESY, Hamburg, Germany) at 20 °C using a Pilatus 2M detector and synchrotron radiation with a wavelength of $\lambda = 0.1\text{ nm}$. The sample-detector distance was 3 m, allowing for measurements in the q -range interval from 0.11 to 4.4 nm^{-1} . The q range was calibrated using the diffraction patterns of silver behenate. The experimental data were normalized to the incident beam intensity and corrected for nonhomogeneous detector response, and the background scattering of the solvent was subtracted. The solvent scattering was measured before and after the sample scattering to control for possible sample holder contamination. Eight consecutive frames comprising the measurement of the solvent, sample, and solvent were performed. No measurable radiation damage was detected by the comparison of eight successive time frames with 15 s exposures. The final scattering curve was obtained using the PRIMUS program by averaging the scattering data collected from the different frames. The automatic sample changer for sample volume 15 μL and filling cycle of 20 s was used.

pH Titration

The pH titration was employed in order to determine the exact pK_a of the DPA block in the PHPMA₂₅-*b*-PDPA₁₀₆ block copolymer at simulated physiological conditions. The block copolymer sample ($c = 0.2\text{ mg}\cdot\text{mL}^{-1}$) was previously dissolved in Milli-Q water. The pH was pre-set to pH = 2.0 by adding small amounts of 0.1 $\text{mol}\cdot\text{L}^{-1}$ HCl solution and the ionic strength was set to 0.15 $\text{mol}\cdot\text{L}^{-1}$ by adding NaCl to the system. A MPT2 autotitrator connected to a Nano-ZS, Model ZEN3600 (Malvern, UK) zetasizer was used for automated measurement of the pH dependencies of the scattering intensity (I_s) and zeta potential (ζ). The I_s and ζ -potential were measured at an angle of 173° using a He-Ne 4.0 mW power laser operating at a wavelength of 633 nm. The equipment measures the electrophoretic mobility (U_E) of the solution and converts the value to ζ -potential (mV) through the Henry's equation. The Henry's function was calculated through the Smoluchowski approximation using the DTS (Nano) program.

Cryogenic transmission electron microscopy (Cryo-TEM)

For cryo-TEM studies, a sample droplet of 2 μL was put on a lacey carbon film covered copper grid (Science Services, Munich, Germany), which was hydrophilized by glow discharge for 15 s. Most of the liquid was then removed with blotting paper, leaving a thin film stretched over the lace holes. The specimens were instantly shock frozen by rapid immersion into liquid ethane and cooled to approximately 90 K by liquid nitrogen in a temperature-controlled freezing unit (Zeiss Cryobox, Zeiss NTS GmbH, Oberkochen, Germany). The temperature was monitored and kept constant in the chamber during all the sample preparation steps. After the specimens were frozen, the remaining ethane was removed using blotting paper. The specimen was inserted into a cryo transfer holder (CT3500, Gatan, Munich, Germany) and transferred to a Zeiss EM922 Omega energy-filtered TEM (EFTEM) instrument (Zeiss NTS GmbH, Oberkochen, Germany). Examinations

were carried out at temperatures around 90 K. The TEM instrument was operated at an acceleration voltage of 200 kV. Zero-loss-filtered images ($\Delta E = 0$ eV) were taken under reduced dose conditions ($100\text{--}1000$ e/nm²). All images were recorded digitally by a bottom-mounted charge-coupled device (CCD) camera system (Ultra Scan 1000, Gatan, Munich, Germany) and combined and processed with a digital imaging processing system (Digital Micrograph GMS 1.8, Gatan, Munich, Germany). All images were taken very close to focus or slightly under the focus (some nanometers) due to the contrast enhancing capabilities of the in-column filter of the used Zeiss EM922 Omega. In EFTEMs, deep underfocussed images can be totally avoided.

Preparation of the nanoparticles

To 2.5 mL of a solution of PHPMA₂₅-*b*-PDPA₁₀₆ ($20\text{ mg}\cdot\text{mL}^{-1}$) and paclitaxel ($500\text{ }\mu\text{g}\cdot\text{mL}^{-1}$) in ethanol 5.0 mL of PBS were added as precipitant. The increase in polarity of the solvent led to the aggregation of the polymer chains forming the NP. The remaining ethanol was removed by evaporation and the final volume of the NPs was concentrated to $5\text{ mg}\cdot\text{mL}^{-1}$. Drug-free NPs were prepared by the same way without adding paclitaxel.

Paclitaxel (PTX) drug loading and loading efficiency

The total amount of the chemotherapeutic PTX loaded into the nanoparticles was measured by HPLC (Shimadzu, Japan) using a reverse-phase column Chromolith Performance RP-18e ($100 - 4.6$ mm, eluent water-acetonitrile with acetonitrile gradient $0\text{--}100$ vol%, flow rate = $1.0\text{ mL}\cdot\text{min}^{-1}$). Firstly $200\text{ }\mu\text{L}$ of the drug loaded NPs were collected from the bulk sample, filtered ($0.45\text{ }\mu\text{m}$) and diluted to $150\text{ }\mu\text{L}$ with HCl ($0.05\text{ mol}\cdot\text{L}^{-1}$). Such procedure led to a final pH ~ 3.0 and therefore a pH-induced NPs disassembly was achieved. Subsequently, the aliquot was diluted to a final volume of 1.0 mL by using acetonitrile ($650\text{ }\mu\text{L}$).¹⁵ Afterwards, $20\text{ }\mu\text{L}$ of the final sample was injected through a sample loop. PTX was detected at 227 nm using ultraviolet (UV) detection. The retention time of PTX was 12.20 min in such experimental conditions. An analytical curve with linear response in the range ($0.5 - 100\text{ }\mu\text{g}\cdot\text{mL}^{-1}$) was obtained and used to determined PTX contents. The drug-loading content (LC) and the drug-loading efficiency (LE) were calculated by using the following equations:

$$LC(\%) = \frac{\text{drug amount in NPs}}{\text{mass of NPs}} \times 100 \quad (\text{eq. 5})$$

$$LE(\%) = \frac{\text{drug amount in NPs}}{\text{drug feeding}} \times 100 \quad (\text{eq. 6})$$

Release Experiments

The release experiments were carried out at $37\text{ }^{\circ}\text{C}$ in pH-adjusted release media (pH 7.4 and 5.0). Aliquots ($500\text{ }\mu\text{L}$) of PTX-NPs were loaded into 36 Slide-A-Lyzer MINI dialysis microtubes with MWCO 10 kDa (Pierce, Rockford, IL). These microtubes were dialyzed against 4 L of PBS (pH 7.4 and 5.0).^{16,23} The release media was changed periodically to reduce the possibility of drug-diffusion equilibrium. The drug release experiments were done in triplicate. At each sampling time, three microtubes were removed from the dialysis system and 0.1 mL from each microtube was sampled and

the remaining drug was extracted by using the aforementioned methodologies. The reported data are expressed as the amount of released PTX relative to the total PTX content in the PTX-NPs.

Stability of the nanoparticles in blood plasma

The stability of the nanoparticles in blood plasma was monitored in real time while incubating them with diluted human plasma (10% v/v in PBS). Typically, $1\text{ mg}\cdot\text{mL}^{-1}$ of the block copolymer nanoparticles was added to a 10% v/v of diluted human plasma in PBS. The dynamic light scattering experiments were performed at interval for a total incubation time of 36 h .^{16,22,23,26}

Cytotoxicity assays

The HeLa cells were cultivated in Dulbecco's Modified Eagle's Medium (DMEM) supplemented with 10% fetal calf serum, 100 units of penicillin and $100\text{ }\mu\text{g}\cdot\text{mL}^{-1}$ of streptomycin (Life Technology, CZ). The cells were grown in a humidified incubator at $37\text{ }^{\circ}\text{C}$ with 5% CO₂. For the cytotoxicity assay, 5000 cells per well were seeded in duplicates in 96 flat bottom well plates in $100\text{ }\mu\text{L}$ of media 24 h before adding the NPs. For adding of the particles the volume was calibrated to $80\text{ }\mu\text{L}$, and $20\text{ }\mu\text{L}$ of the 5-times concentrated dilution of PTX or particle dispersion were added per well to a final PTX concentration ranging from 10^{-5} to $5\text{ }\mu\text{g}\cdot\text{mL}^{-1}$. All dilutions were made in full incubation medium under thorough mixing of each dilution step. The sample concentrations of the PTX-loaded particles were adjusted to contain the same total amount of PTX as the samples with free PTX. The cells were incubated with free drug or NPs for 24 h or 48 h . Then $10\text{ }\mu\text{L}$ of alamarBlue® cell viability reagent (Life Technologies, Czech Republic) were added to each well and incubated a minimum for 3 h at $37\text{ }^{\circ}\text{C}$. The fluorescence of the reduced marker dye was read with a Synergy H1 plate reader (BioTek Instruments, US) at excitation 570 and emission 600 nm . The fluorescence intensity of the control samples (with no drug or particles added) was set as a marker of 100% cell viability. The fluorescence signal of "0% viability samples" (were all cells were killed by addition of hydrogen peroxide) was used as background and subtracted from all values prior to calculations. The non-toxic character of the blank particles without drug was shown by incubation of cells with the $0.4\text{ mg}\cdot\text{L}^{-1}$ of blank particles. This corresponds to the amount of polymer that is contained in the samples of drug-loaded particles with $5\text{ }\mu\text{g}\cdot\text{L}^{-1}$ total PTX content. For the cell experiments the PTX-dilutions in incubation medium were made from a PTX stock solution of $120\text{ }\mu\text{g}\cdot\text{mL}^{-1}$ in PBS/DMSO ($96.5 : 3.5$ v/v).⁴⁴ Precipitation of the hydrophobic PTX out of the cell culture medium can therefore be excluded because the PTX was previously fully dissolved in a PBS/DMSO solution ($96.5 : 3.5$ v/v) and subsequently diluted in the serum-supplied medium under thorough mixing. Consequently, even at maximal PTX-concentration of $5\text{ }\mu\text{g}\cdot\text{mL}^{-1}$, the final DMSO concentration in the incubation medium was below 0.2% and therefore no effect on cell vitality in the applied setup.⁴⁵ All the cells experiments are average of at least 4 measurements ($n \geq 4$).

Acknowledgements

This research was supported by the Norwegian Financial Mechanism 2009-2014 under Project contract no 7F14009.

ARTICLE

Journal Name

C.R.-E. acknowledges Grant Agency of the Czech Republic (GACR) under contract no. 15-09368Y and the project "BIOCEV – Biotechnology and Biomedicine Centre of the Academy of Sciences and Charles University" (CZ.1.05/1.1.00/02.0109), from the European Regional Development Fund. M. D. acknowledges BIMF (Bayreuth Institute of Macromolecular Research) and BZKG (Bayreuth Center for Colloids and Interfaces) for financial support. F.N. acknowledges support through the CNRS project PICS No. 06130.

Notes and references

- J. Rodríguez-Hernández, F. Chécot, Y. Gnanou, S. Lecommandoux, *Prog. Polym. Sci.*, 2005, **30**, 691.
- Y. Mai and A. Eisenberg, *Chem. Soc. Rev.*, 2012, **41**, 5969.
- T. Smart, H. Lomas, M. Massignani, M. V. Flores-Merino, L. R. Perez and G. Battaglia, *Nano Today* 2008, **3**, 38.
- L. Zhang and A. Eisenberg, *J. Am. Chem. Soc.*, 1996, **118**, 3168.
- L. Zhang and A. Eisenberg, *Polym. Adv. Technol.*, 1998, **9**, 677.
- A. Blanazs, S. P. Armes, A. J. Ryan, *Macromol. Rapid Commun.*, 2009, **30**, 267.
- G. Gaucher, M.-H. Dufresne, V. P. Sant, N. Kang, D. Maysinger, J.-C. Leroux, *J. Control. Release* 2005, **109**, 169.
- V. P. Chauhan and R. K. Jain, *Nature Mater.*, 2013, **12**, 958.
- S. Petrova, E. Jäger, R. Konefał, A. Jäger, C. G. Venturini, J. Špěváček, E. Pavlova and P. Štěpánek, *Polym. Chem.*, 2014, **5**, 3884.
- Q. Yin, J. Shen, Z. Zhang, H. Yu and Y. Li, *Adv. Drug Deliv. Rev.*, 2013, **65**, 1699.
- B. A. Webb, M. Chimenti, M. P. Jacobson and D. L. Barber, *Nat. Rev. Cancer* 2011, **11**, 671.
- E. G. Kelley, J. N. L. Albert, M. O. Sullivan and T. H. Epps III, *Chem. Soc. Rev.*, 2013, **42**, 7057.
- E. S. Lee and Y. H. Bae, *J. Control. Release* 2008, **132**, 164.
- K. Zhou, H. Liu, S. Zhang, X. Huang, Y. Wang, G. Huang, B. D. Sumer and J. Gao, *J. Am. Chem. Soc.*, 2012, **134**, 7803.
- Y. Wang, K. Zhou, G. Huang, C. Hensley, X. Huang, X. Ma, T. Zhao, B. D. Sumer, R. J. DeBerardinis and J. Gao, *Nature Mater.*, 2014, **13**, 204.
- F. C. Giacomelli, P. Štěpánek, C. Giacomelli, V. Schmidt, E. Jäger, A. Jäger and K. Ulbrich, *Soft Matter* 2011, **7**, 9316.
- C. Pegoraro, D. Cecchin, L. S. Gracia, N. Warren, J. Madsen, S. P. Armes, A. Lewis, S. MacNeil and G. Battaglia, *Cancer Lett.*, 2013, **334**, 328.
- J. Fang, H. Nakamura, H. Maeda, *Adv. Drug Deliv. Rev.*, 2011, **63**, 136.
- T. Riedel, Z. Riedelová-Reicheltová, P. Májek, C. Rodríguez-Emmenegger, M. Houska, J.E. Dyr and E. Brynda, *Langmuir*, 2013, **29**, 3388.
- C. Rodríguez-Emmenegger, E. Brynda, T. Riedel, M. Houska, V. Šubr, A. B. Alles, E. Hasan, J.E. Gautrot and W. T. S. Huck, *Macromol. Rapid Commun.*, 2011, **32**, 952.
- F. Surman, T. Riedel, M. Bruns, N.Y. Kostina and C. Rodríguez-Emmenegger, *Macromol. Biosci.*, 2015, DOI: 10.1002/mabi.201400470.
- E. Jäger, A. Jäger, T. Etrych, F. C. Giacomelli, P. Chytil, A. Jigounov, J.L. Putaux, B. Říhová, K. Ulbrich and P. Štěpánek, *Soft Matter* 2012, **8**, 9563.
- E. Jäger, A. Jäger, P. Chytil, T. Etrych, F. C. Giacomelli, B. Říhová, P. Štěpánek and K. Ulbrich, *J. Control. Release* 2013, **165**, 153.
- B. Angelov, A. Angelova, S.K. Filippov, T. Naryanan, M. Drechsler, P. Štěpánek, P. Couvreur and S. Lesieur, *J. Phys. Chem. Lett.*, 2013, **4**, 1959.
- B. Angelov, A. Angelova, S.K. Filippov, G. Karlsson, N. Terril, S. Lesieur and P. Štěpánek, *Soft Matter* 2011, **7**, 9714.
- F.C. Giacomelli, P. Štěpánek, V. Schmidt, E. Jäger, A. Jäger and C. Giacomelli, *Nanoscale* 2012, **4**, 4504.
- C. Giacomelli, L. Le Men and R. Borsali, *Biomacromolecules* 2006, **7**, 817.
- C.E. de Castro, B. Mattei, K.A. Riske, E. Jäger, A. Jäger, P. Štěpánek, F.C. Giacomelli, *Langmuir* 2014, **30**, 9770.
- H. Cabral, Y. Matsumoto, K. Mizuno, Q. Chen, M. Murakami, M. Kimura, Y. Terada, M.R. Kano, K. Miyazono, M. Uesaka, N. Nishiyama and K. Kataoka, *Nat. Nanotechnol.*, 2011, **6**, 815.
- K.R. Whiteman, V. Šubr, K. Ulbrich and V.P. Torchilin, *J. Liposome Res.*, 2001, **11**, 153.
- S. Kamei and J. Kopeček, *Pharm. Res.*, 1995, **12**, 663.
- K. Cho, X. Wang, S. Nie, Z. Chen and D.M. Shin, *Clin. Cancer Res.*, 2008, **14**, 1310.
- J.E. Liebmman, J.A. Cook, C. Lipschultz, D. Teague, J. Fisher and J.B. Mitchell, *Br. J. Cancer* 1993, **68**, 1104.
- X. Peng, F. Gong, Y. Chen, Y. Jiang, J. Liu, M. Yu, S. Zhang, M. Wang, G. Xiao and H. Liao, *Cell Death & Disease* 2014, **5**, e1367.
- D. Li, Y. Zhang, S. Jin, J. Guo, H. Gao and C. Wang, *J. Mater. Chem. B.*, 2014, **2**, 5187.
- F. Danhier, N. Lecouturier, B. Vroman, C. Jerome, J. Marchand-Brynaert, O. Feron and V. Preat, *J. Control. Release* 2009, **133**, 11.
- J. Panyam, W.Z. Zhou, S. Prabha, S.K. Sahoo and V. Labhasetwar, *FASEB J.*, 2002, **16**, 1217.
- S.K. Sahoo, J. Panyam, S. Prabha and V. Labhasetwar, *J. Control. Release* 2002, **82**, 105.
- G. Gaucher, R.H. Marchessault and J.-C., Leroux, *J. Control. Release* 2010, **143**, 2-12.
- W.T. Godbey, K.K. Wu and A.G. Mikos, *Proc. Natl. Acad. Sci. U.S.A.*, 1999, **96**, 5177.
- K. Ulbrich, V. Šubr, J. Strohalm, D. Plocová, M. Jelínková and B. Říhová, *J. Control. Release* 2000, **64**, 63.
- S. Perrier, P. Takolpuckdee and C.A. Mars, *Macromolecules* 2005, **38**, 2033.
- J. Jakes, *Czech. J. Phys.*, 1988, **38**, 1305.
- E.A. Dubikovskaya, S.H. Thorne, T.H. Pillow, C.H. Contag and P.A. Wender, *Proc. Natl. Acad. Sci. U.S.A* 2008, **105**, 12128.
- A. B. Trivedi, N. Kitabatake, E. Do, *Agr. Biol. Chem.*, 1990, **54**, 2961.